

Spin-valley lifetimes in a silicon quantum dot with tunable valley splitting

C. H. Yang,¹ A. Rossi,^{1,*} R. Ruskov,² N. S. Lai,¹ F. A. Mohiyaddin,¹
S. Lee,³ C. Tahan,² G. Klimeck,³ A. Morello,¹ and A. S. Dzurak¹

¹*Australian Research Council Centre of Excellence for Quantum Computation and Communication Technology,
School of Electrical Engineering & Telecommunications,
The University of New South Wales, Sydney 2052, Australia*

²*Laboratory for Physical Sciences, 8050 Greenmead Dr., College Park, MD 20740, USA*

³*Network for Computational Nanotechnology, Birck Nanotechnology Center,
Purdue University, West Lafayette, IN 47907, USA*

(Dated: February 6, 2013)

Whilst silicon is a promising material for quantum computation, the degeneracy of the conduction band minima (valleys) must be lifted with a splitting sufficient to ensure formation of well-defined and long-lived spin qubits. Here we demonstrate that valley separation can be accurately tuned via electrostatic gate control in a metal-oxide-semiconductor quantum dot, providing splittings spanning 0.3 - 0.8 meV. The splitting varies linearly with applied electric field, with a ratio in agreement with atomistic tight-binding predictions. We demonstrate single-shot spin readout and measure the spin relaxation for different valley configurations and dot occupancies, finding one-electron lifetimes exceeding 2 seconds. Spin relaxation occurs via phonon emission due to spin-orbit coupling between the valley states, a process not previously anticipated for silicon quantum dots. An analytical theory describes the magnetic field dependence of the relaxation rate, including the presence of a dramatic rate enhancement (or hot-spot) when Zeeman and valley splittings coincide.

I. INTRODUCTION

Silicon is at the heart of all modern microelectronics. Its properties have allowed the semiconductor industry to follow Moore's law for nearly half a century, delivering nowadays billions of nanometre-scale transistors per chip. Remarkably, silicon is also an ideal material to manipulate quantum information encoded in individual electron spins¹⁻³. This is a consequence of the weak spin-orbit coupling and the existence of an abundant spin-zero isotope, which can be further enriched to obtain a "semiconductor vacuum" in which an electron spin can preserve a coherent quantum superposition state for exceptionally long times⁴.

In order to define a robust spin- $1/2$ qubit Hilbert space, it is necessary that the energy scale of the two-level system is well separated from higher excitations. In this respect, a major challenge for the use of silicon is represented by the multi-valley nature of its conduction band. In a bulk silicon crystal the conduction band minima are six-fold degenerate, but in a two-dimensional electron gas (2DEG), the degeneracy is broken⁵ into a two-fold degenerate ground state (Γ valleys) and a four-fold degenerate excited state (Δ valleys), due to vertical confinement of electrons with different effective mass along the longitudinal and transverse directions, respectively. Furthermore, the Γ valley degeneracy is generally lifted by a sharp perpendicular potential⁶⁻⁹ and the relevant energy separation is termed the valley splitting (VS).

The valley splitting depends on physics at the atomic scale¹⁰⁻¹² (e.g. roughness, alloy and interface disorder), and so it is not surprising that experiments have revealed a large variability of splittings among devices, ranging from hundreds of μeV ^{5,13-15} up to tens of meV in exceptional cases¹⁶. At present, the lack of a reliable experi-

mental strategy to achieve control over the VS is driving an intense research effort for the development of devices that can assure robust electron spin qubits by minimising multi-valley detrimental effects^{17,18}, or even exploit the valley degree of freedom^{19,20} for new types of qubits.

Another crucial parameter to assess the suitability of a physical system to encode spin-based qubits is the relaxation time of spin excited states (T_1). Spin lifetimes have been measured for gate-defined Si quantum dots (QDs)²¹, Si/SiGe QDs^{22,23} and donors in Si²⁴, reporting values which span from a few milliseconds to a few seconds. Furthermore, the dependence of the spin relaxation rate (T_1^{-1}) on an externally-applied magnetic field (B) has been investigated. Different mechanisms apply to donors and QDs, accounting for observed $T_1^{-1} \propto B^5$ and B^7 dependencies²⁵, respectively. In principle, $T_1^{-1}(B)$ depends on the valley configuration and the details of the excited states above the spin ground state. However, until now, no experimental observation of the effects of a variable VS on the relaxation rate has been reported.

Here, we demonstrate for the first time that the valley splitting in a silicon QD can be finely tuned by direct control of an electrostatic gate potential. We find that the dependence of the VS on vertical electric field at the Si/SiO₂ interface is strikingly linear, and show that its tunability is in excellent agreement with atomistic tight-binding predictions. We demonstrate accurate control of the VS over a range of about 500 μeV and use it to explore the physics of spin relaxation for different QD occupancies ($N=1, 2, 3$). We probe both the regime where the VS is much larger than the Zeeman splitting at all magnetic fields and that where the valley and spin splittings are comparable. We observe a dramatic enhancement of the spin decay rate (relaxation hot-spot) when spin and valley splittings coincide. To our knowledge, such hot-

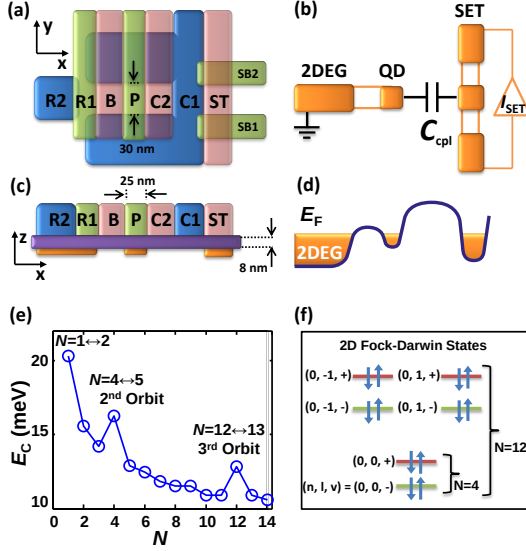


FIG. 1: Device architecture and addition energy spectrum. (a) Schematic (top view) of the device's gate layout. Different colours represent different layers within the gate stack. (b) Schematic diagram of the single-lead QD (left) and SET detector (right). Regions where an electron layer is formed are coloured in orange. The readout signal (I_{SET}) is sensitive to the QD charge state due to the QD/SET capacitive coupling (C_{cpl}). (c) Device cross-sectional schematic. An electron layer is formed underneath the positively biased gates: R1 and R2 define the QD reservoir; P controls the QD population; and ST the sensor's island. The SiO_2 layer (in purple) thickness and plunger gate width are indicated. (d) Energy diagram showing qualitatively the conduction band profile in the device. Electrons accumulate wherever the gate bias lowers the conduction band below the Fermi level, E_F . (e) Charging energy as a function of electron number. Spikes corresponding to complete 2D shell filling are observed. (f) Schematic of electron filling for two-valley 2D Fock-Darwin states. Each state can hold two electrons of antiparallel spin and is identified by a pair of quantum numbers (n, l) and its valley occupancy (v) .

spots (HS) have been predicted for relaxation involving orbital states^{26,27}, but they are yet to be observed. We develop an analytic theory that explains the B -field dependence of the relaxation rates and the details of the relaxation HS in terms of admixing of spin-valley states. This mechanism is seen to be significantly more prominent than the conventional spin-orbit hybridization²⁸.

II. QD ADDITION SPECTRUM

Our device is fabricated using a multi-level gated metal-oxide-semiconductor (MOS) technology²⁹, and its architecture is depicted in Fig. 1(a)-(d). A quantum dot is formed under gate P by applying a positive bias voltage to induce an electron accumulation layer. Strong planar

confinement for the dot's potential well is achieved by negatively biasing gates B, C1 and C2. A 2DEG reservoir is also induced by positively biasing gates R1 and R2, and the QD occupancy can be modified by inducing electrons to tunnel between this reservoir and the dot. The remaining gates, namely SB1, SB2, ST, are employed to define a single-electron transistor (SET), capacitively coupled to the QD and used as a read-out device. The high flexibility of our design would allow us to use the same device also as a (single-lead) double dot structure by rearranging the gate bias (e.g. dots can be formed under gates B and C2). However, in this work, we only present results relevant to the single-dot configuration.

In order to characterize the addition spectrum of the QD, we make use of a technique previously developed for GaAs-based systems which combines charge detection and gate pulsing³⁰. There is no direct transport through the single-lead QD and, therefore, addition/removal of charge is only detected via modifications in the SET current. In particular, charge transitions are detected as current peaks in the SET signal whenever the QD energy eigenstates come into resonance with the reservoir's Fermi level. Note that the SET-QD coupling is merely capacitive (via C_{cpl}) and electrons do not tunnel between them. In order to maximize charge sensitivity in the detector, we employ dynamic voltage compensation³¹ on different gates which makes our read-out signal virtually unaffected by slow charge drifts and random charge rearrangements.

Fig. 1(e) illustrates the addition energy spectrum for the first fourteen electron additions to the QD. There is very little variation of charging energy (E_C) for high occupancies, i.e. $E_C \approx 11$ meV for $N > 9$. However, by decreasing the electron number, the charging energy steadily increases, as expected when the dot size is significantly affected by the electron number. This evidently indicates that the few-electron regime has been achieved. Most interestingly, the energy spectrum shows peaks for the addition of the 5th and 13th electrons. The extra addition energy needed for those transitions can be attributed to complete filling of the first and second orbital shells. As illustrated in Fig. 1(f), this is consistent with the energy spectrum of two-valley 2D Fock-Darwin states³², where the first and second orbital shells hold 4 and 8 electrons respectively. This confirms that we can probe the occupancy until the last electron. To our knowledge, such a neat manifestation of two-dimensional shell structure has been observed before only in InGaAs dots³³ and in Si/SiGe dots³⁴. It is remarkable that our MOS-based planar architecture can show such a degree of circular symmetry. This is likely due to both our gate design (leading to symmetric dot confinement) and excellent quality of the thin gate oxide.

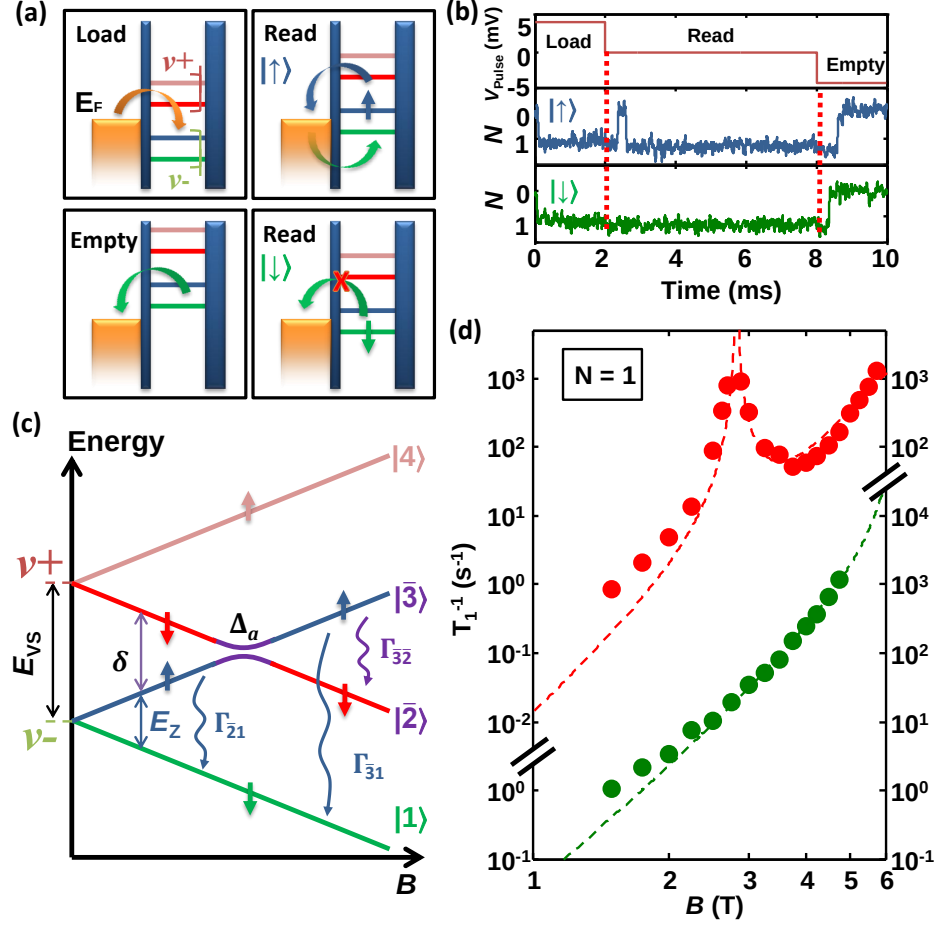


FIG. 2: Spin readout and relaxation rates for single-electron occupancy. (a) Schematic diagram showing the effect of the 3-level pulse sequence on the electro-chemical potential of the dot. Energy levels in the QD are Zeeman split according to spin polarisation and valley degeneracy is lifted. For clarity, only lower valley states are shown to be loaded/unloaded. (b) Pulsing sequence (top) for the single-shot spin readout and normalised SET signal for spin-up (middle) and spin-down (bottom). (c) Energy diagram of the 1-electron spin-valley states as a function of B -field. Maximum mixing of spin and valley degrees of freedom occurs at the anticrossing point where Zeeman and valley splittings coincide. Relevant relaxation processes are sketched. (d) Relaxation rates as a function of magnetic field for different valley splittings. Data points for $E_{VS} = 0.75$ meV, $E_{VS} = 0.33$ meV are shown as green and red circles, respectively. Dashed lines are the calculated relaxation rates fitted with $r=1.7$ nm (green), $r=1.1$ nm (red).

III. SPIN-VALLEY LIFETIMES

In order to measure the spin state of individual electrons in the QD, we use an energy-selective readout technique³⁵. The readout protocol consists of three phases clocked by a three-level pulsed voltage applied to gate P which directly controls the dot's electrochemical potential [see Fig. 2 (a)]. Firstly, an electron of unknown spin is loaded into the dot causing a sudden decrease

in the sensor current. Next, the potential of the dot is lifted so that the Fermi level of the reservoir lies between the spin-up and spin-down states of the dot, meaning that a spin-up electron can tunnel off the dot while a spin-down electron is blocked. This is the read phase, during which the presence of a spin-up state would be signalled by a current transient (spin-up tunnels out and then spin-down tunnels in) whereas a spin-down electron would lead to no current modification. Finally, the dot's potential is further lifted to allow the electron to tunnel

off, regardless of its spin orientation. In Fig. 2 (b) single-shot traces for both spin-up (in blue) and spin-down (in green) detection are plotted. The longer the system is held in the load phase before performing a read operation, the more likely it is for the spin-up excited state to decay to the spin-down ground state. Thus, by varying the length of the load phase and monitoring the probability of detecting a spin-up electron, we can determine^{24,35} the spin lifetime, T_1 . In our experiments the B -field is directed along the [110] crystallographic axis. As shown in Fig. 2 (d), we observe a wide range of spin lifetimes as a function of magnetic field, with lifetimes as long as 2.6s at the lowest fields studied, $B=1.25$ T. These are some of the largest lifetimes observed to date in silicon quantum dots²⁵.

A key focus of our experiment was to electrostatically tune the valley energy separation and measure relaxation rates in different valley configurations and QD electron occupancies. *As we show below, our data definitively indicate that excited valley states play a critical role in the spin relaxation processes.* We develop a theory to explain how changes in the valley splitting affects the spin-valley state mixing and leads to the observed relaxation times.

As we detail in Section IV, we have attained accurate gate control of the valley splitting, allowing us to tune it over a range of hundreds of μ eV. This permits us to conduct experiments in regimes where the valley splitting (E_{VS}) is either larger or smaller than the Zeeman spin splitting (E_Z), depending on the magnitude of the magnetic field [see Fig. 2 (c)].

Fig. 2 (d) presents measurements of spin relaxation rates as a function of magnetic field for two valley splitting values at a fixed dot population of $N = 1$. We start by examining a configuration where the valley separation is larger than the spin splitting at all fields (green data set). In other words, we operate in a regime for which

$$E_{VS} > E_Z = g\mu_B B \quad (1)$$

where g is the electron gyromagnetic ratio, μ_B is the Bohr magneton and B is the applied in-plane magnetic field.

For $E_{VS}=0.75$ meV [green data in Fig. 2 (d)], we observe a monotonic increase of the rate with respect to B that becomes increasingly fast as E_Z approaches E_{VS} . In our experimental conditions, the $T_1^{-1} \propto B^5$ dependences for known mechanisms in silicon should not apply^{36,37}, while predicted^{23,25,27,38} rates $\propto B^7$ do not explain the experimental data.

By decreasing the valley separation to $E_{VS}=0.33$ meV, we can achieve the condition where the Zeeman splitting matches or exceeds the valley splitting. The red data in Fig. 2 (d) illustrate the situation where inequality (1) only holds for $B < 2.8$ T. When $E_Z = E_{VS}$ (i.e. for $B=2.8$ T), a spike in the relaxation rate occurs. Relaxation hot-spots have been previously predicted to occur for spin relaxation involving orbital states in single and coupled QDs^{26,27,39,40}. *To our knowledge, this is the first experimental observation of such a phenomenon.*

In order to understand the relaxation mechanisms, we

have developed a model that takes into account the perturbations in pure spin states due to spin-orbit coupling (SOC), yielding eigenstates which are admixtures of spin and valley states. The four lowest spin-valley states [see Fig. 2(c)] are defined as $|1\rangle = |v_-, \downarrow\rangle$, $|2\rangle = |v_-, \uparrow\rangle$, $|3\rangle = |v_+, \downarrow\rangle$, $|4\rangle = |v_+, \uparrow\rangle$. These states are considered to be only very weakly affected by higher excitations, such as orbital levels which are at least 8 meV above the ground state in our device⁴¹. In practice, mixing to a $2p$ -like orbital state leads to a B^7 dependence in T_1^{-1} and is, therefore, important mainly for high B -fields (above the anticrossing point). At lower fields, the prominent mechanism is the spin-valley admixing, which we now discuss in detail.

The relaxation between pure spin states is forbidden because the electron-phonon interaction does not involve spin flipping. However, in the presence of interface disorder, SOC can mix states that contain both the valley and spin degrees of freedom, thus permitting phonon-induced relaxation. Indeed, in the non-ideal case of QDs with a disordered interface, roughness can perturb the envelope function of both valleys (otherwise identical for ideal interfaces) and allows one to assume non-zero dipole matrix elements, such as $\mathbf{r}_{-+} \equiv \langle v_- | \mathbf{r} | v_+ \rangle$, $\mathbf{r}_{--} \equiv \langle v_- | \mathbf{r} | v_- \rangle$, $\mathbf{r}_{++} \equiv \langle v_+ | \mathbf{r} | v_+ \rangle$. By means of perturbation theory, we define renormalized excited states $|\bar{2}\rangle$ and $|\bar{3}\rangle$ that relax to the ground state $|1\rangle$. The leading order corrections to the wavefunctions are given by:

$$|\bar{2}\rangle^{(0)} = \sin \frac{\gamma}{2} |2\rangle - \cos \frac{\gamma}{2} |3\rangle \quad (2)$$

$$|\bar{3}\rangle^{(0)} = \cos \frac{\gamma}{2} |2\rangle + \sin \frac{\gamma}{2} |3\rangle \quad (3)$$

where $\cos \frac{\gamma}{2} \equiv [\frac{1+a}{2}]^{1/2}$, $\sin \frac{\gamma}{2} \equiv [\frac{1-a}{2}]^{1/2}$, and $a \equiv -\delta / \sqrt{\delta^2 + \Delta_a^2}$ is an expression involving the detuning from the anticrossing point, $\delta \equiv E_{VS} - E_Z$, and the energy splitting at the anticrossing, Δ_a .

By evaluating the relaxation rate via the electron-phonon deformation potential interaction, we obtain the rate below the anticrossing as:

$$\Gamma_{\bar{2}1} = \cos^2 \frac{\gamma}{2} \Gamma_{v'v} = \frac{\sqrt{\delta^2 + \Delta_a^2} - \delta}{2\sqrt{\delta^2 + \Delta_a^2}} \Gamma_{v'v} \quad (4)$$

where $\Gamma_{v'v} \equiv \Gamma_{v'v}(\Delta E_{v'v}, \mathbf{r}_{-+})$ is the pure valley relaxation rate that depends on the energy difference relevant to the transition and the dipole matrix element. The experimental condition for which the hot-spot occurs (i.e. $E_{VS} = E_Z$) is modelled as an anticrossing point for the mixed states $|\bar{2}\rangle$ and $|\bar{3}\rangle$. At that point, spin relaxation is maximized and $\Gamma_{\bar{2}1}$ approaches the valley relaxation rate, as $\delta \rightarrow 0$ in eq. (4).

Above the anticrossing (i.e. $E_{VS} < E_Z$), the relevant relaxation transitions are $|\bar{3}\rangle \rightarrow |1\rangle$ and $|\bar{3}\rangle \rightarrow |\bar{2}\rangle$ (the subsequent decay $|\bar{2}\rangle \rightarrow |1\rangle$ is in the form of a fast inter-valley transition and is, therefore, neglected). The ana-

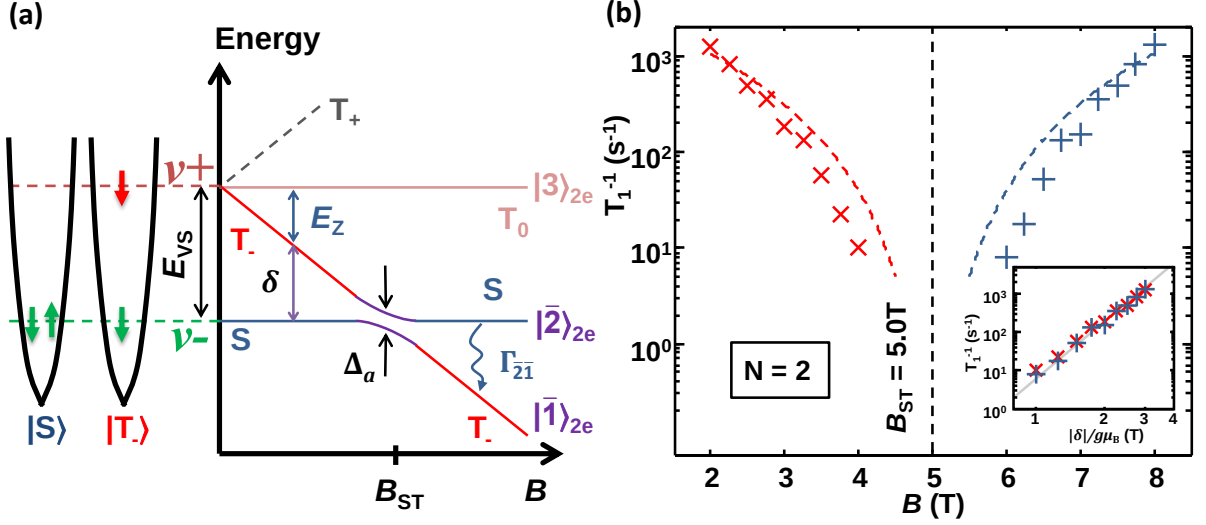


FIG. 3: Spin-valley relaxation for 2-electron occupancy. (a) Energy diagrams of the 2-electron spin-valley states in the dot's potential well (left) and as a function of B -field (right). Dashed line indicates that T_+ is not accessible (see text). (b) Relaxation rate as a function of B -field for $N = 2$ and $E_{VS} = 0.58\text{meV}$. Red (blue) crosses represent data points at fields smaller (larger) than the anticrossing point. Dashed lines are the calculated rates fitted with $r^{2e}=4.76\text{ nm}$. Inset: Data from the main graph re-plotted as a function of the modulus of the detuning energy, δ . Points of equal absolute detuning have nearly the same decay rates. δ^5 dependence (grey line) is a guide for the eye.

lytical formulations of these contributions read:

$$\Gamma_{31} = \sin^2 \frac{\gamma}{2} \Gamma_{v'v} = \frac{\sqrt{\delta^2 + \Delta_a^2} + \delta}{2\sqrt{\delta^2 + \Delta_a^2}} \Gamma_{v'v} \quad (5)$$

$$\Gamma_{32} = \sin^2 \frac{\gamma}{2} \cos^2 \frac{\gamma}{2} \Gamma_{v'v} (\Delta E_{v'v}, \mathbf{r}_{--} - \mathbf{r}_{++}) \quad (6)$$

The dashed lines in Fig. 2(d) show the calculated relaxation rates relevant to the two experimental values of E_{VS} discussed. We use dipole matrix elements as a single free parameter by assuming $|\mathbf{r}_{-+}| \simeq |\mathbf{r}_{--} - \mathbf{r}_{++}| \equiv r$. A least-square fit to the experimental data is performed by fixing the SOC strength to $(\beta_D - \alpha_R) \approx 45 - 60\text{ m/s}$ (justified by the high electric field $\approx 3 \times 10^7\text{ V/m}$, see Refs. [42,43]), where β_D (α_R) is the Dresselhaus (Rashba) strength. The fit then extracts a dipole size $r \approx 2\text{-}3\text{ nm}$ for all three values of E_{VS} .

The good agreement between the calculations and experiment, as well as the presence of a hot-spot at the point of degeneracy between Zeeman and valley splitting, provide strong evidence of our ansatz that the spin relaxation is predominantly due to a new mechanism: that of mixing with the excited valley states via Rashba/Dresselhaus-like SOC.

We now examine the case $N = 2$ electrons, and investigate the dependence of the relaxation rate on the magnetic field at a fixed valley splitting ($E_{VS}=0.58\text{ meV}$). We note that the energy levels accessible for loading the second electron in the dot, when the $N = 1$ spin-down ground state is already occupied, are either the singlet (S) or the two lower triplets (T_-, T_0), while the higher triplet (T_+) would require a spin-flip and is, therefore, not readily accessible [see Fig. 3(a)]. In general, for triplet states, the antisymmetry of the two-electron wavefunction requires one electron to occupy a higher energy state. For our multi-valley QD [Fig. 1 (f)], this requirement is

fulfilled when the two electrons occupy different valley states [see Fig. 3 (a)]. For low fields, the ground state is S and the triplets have higher energies. This results in excited states (triplets) that extend over two valleys and relax to single-valley ground states (singlets).

As the magnetic field is increased, S and T_- undergo an avoided crossing ($B \equiv B_{ST}$), and then T_- becomes the ground state. We adjust the levels of our pulsed readout protocol so that, during the load phase only S and T_- are below the reservoir's Fermi energy, while, during the read phase, the Fermi energy is positioned within the singlet-triplet (ST) energy gap. As a consequence, for $B < B_{ST}$ ($B > B_{ST}$) a T_- (S) state would be signalled with a current transient, and relaxation rates can be extracted as for the $N = 1$ occupancy. The experimental relaxation rates in Fig. 3(b) show a strongly non-monotonic behaviour, approaching an absolute minimum at the anticrossing point ($B_{ST}=5T$). The trend is strikingly symmetric, as can be appreciated when T_1^{-1} is plotted against the detuning energy, as shown in the inset. This symmetry is reflected in the QD energy spectrum [Fig. 3(a)], as far as the S and T_- states are concerned. For $B < B_{ST}$, the ST energy gap decreases with increasing B , resulting in slower relaxation rates. By contrast, for $B > B_{ST}$, the ST energy gap increases for increasing field, and so does the relaxation rate.

To model the 2-electron case, we build the wavefunctions for S and T_- from the single-particle states by considering the Coulomb interaction as a perturbing averaged field. The corresponding states are defined as $|1\rangle_{2e} = |v_-, v_-, S\rangle$, $|2\rangle_{2e} = |v_-, v_+, T_- \rangle$. Next, the additional perturbation given by SOC leads to renormalized eigenstates which are admixtures of singlet and triplet, and whose leading order approximations read:

$$|\bar{1}\rangle_{2e}^{(0)} = \sin\frac{\gamma}{2} |1\rangle_{2e} - \cos\frac{\gamma}{2} |2\rangle_{2e} \quad (7)$$

$$|\bar{2}\rangle_{2e}^{(0)} = \cos\frac{\gamma}{2} |1\rangle_{2e} + \sin\frac{\gamma}{2} |2\rangle_{2e} \quad (8)$$

being similar forms to eq. (2) (3). By evaluating the electron-phonon Hamiltonian matrix element for the transition between these states, one finds that it coincides with its 1-electron counterpart for $|\bar{3}\rangle_{1e} \rightarrow |\bar{2}\rangle_{1e}$. Therefore, we can conclude that the corresponding relaxation rates have the same functional form as those derived in eq. (6), i.e. $\Gamma_{21}^{2e} = \Gamma_{32}^{1e}$, although the matrix elements for the two cases will be different. Dashed lines in Fig. 3 (b) represent the calculated rates which are fitted to the experimental data similarly to the case $N = 1$. Once again, the model convincingly reproduces the main features of the experimental trend, in particular the rates for fields away from the anticrossing together with the symmetry of the characteristics with respect to B_{ST} . Further work may be needed to improve the fit in the vicinity of the anticrossing point.

We also measured the relaxation rates for $N = 3$ electrons (not shown) and, interestingly, observed nearly

identical rates to the 1-electron case. This may be explained in terms of a negligible effect of the Coulomb interaction on the valley spectrum^{41,44}.

IV. VALLEY SPLITTING CONTROL

We now turn to the experimental demonstration of accurate control of the valley splitting, E_{VS} , via electrostatic gating. To determine E_{VS} , we use two different experimental approaches. One utilizes the rapid increase in spin relaxation at the hot-spot, and is applicable in the low magnetic field regime. The other is based on magnetospectroscopy, and is relevant for high fields.

The first technique stems from the fact that the hot-spot (HS) can be reliably detected by monitoring the spin-up probability as a function of magnetic field. In Fig. 4 (a), we show measurements of the spin-up probability performed with the same method as the one used to evaluate spin lifetimes. We see that the probability of detecting a spin-up electron decreases significantly at some magnetic fields. A sudden drop of the spin-up fraction in a narrow range of field identifies the increase in relaxation rate associated with the HS. Given that valley and Zeeman splittings coincide at the HS, one can extract the valley separation as $E_{VS} = g\mu_B B_{HS}$, where B_{HS} is defined as the field at which the HS is observed. For varying gate voltage configurations, we scan B in the range $2.8T < B < 5T$, and identify B_{HS} by setting an arbitrary probability threshold [green shaded area in Fig. 4(a)] below which the HS is assumed to occur. The use of this technique is limited to $B < 5T$ because the lifetime drop at the HS can be therein confidently assessed. At higher fields the relaxation becomes increasingly fast and its enhancement at the HS is indistinguishable within our measurement bandwidth ($\approx 10KHz$).

In order to evaluate E_{VS} at higher magnetic fields, we use a more conventional magneto-spectroscopic approach, as shown in Fig. 4 (b). By employing the same gate-pulsed technique used for the charge stability experiments, we focus on the singlet-triplet ground state transition as we load the second electron into the dot (i.e. $N = 1 \rightarrow 2$ transition) in the range $5T < B < 6.5T$. This is clearly identified as the point where the S (light grey feature) and T_- (dark grey feature) states cross. Here, $E_{VS} = g\mu_B B_{ST}$, as seen in Fig. 3(a).

The data points in Fig. 4 (c) represent the measured valley separation as a function of V_p , obtained by means of the aforementioned techniques. The solid line fit shows remarkable consistency between the two sets of data and reveals that E_{VS} depends linearly on the gate voltage over a range of nearly $500 \mu eV$, with a slope of $640 \mu eV/V$. To our knowledge, this is the first demonstration of the ability to accurately tune the valley splitting electrostatically in a silicon device.

A linear dependence of the valley splitting with respect to the vertical electric field has been predicted for 2DEG systems via effective mass theory^{7,9,10}. A similar

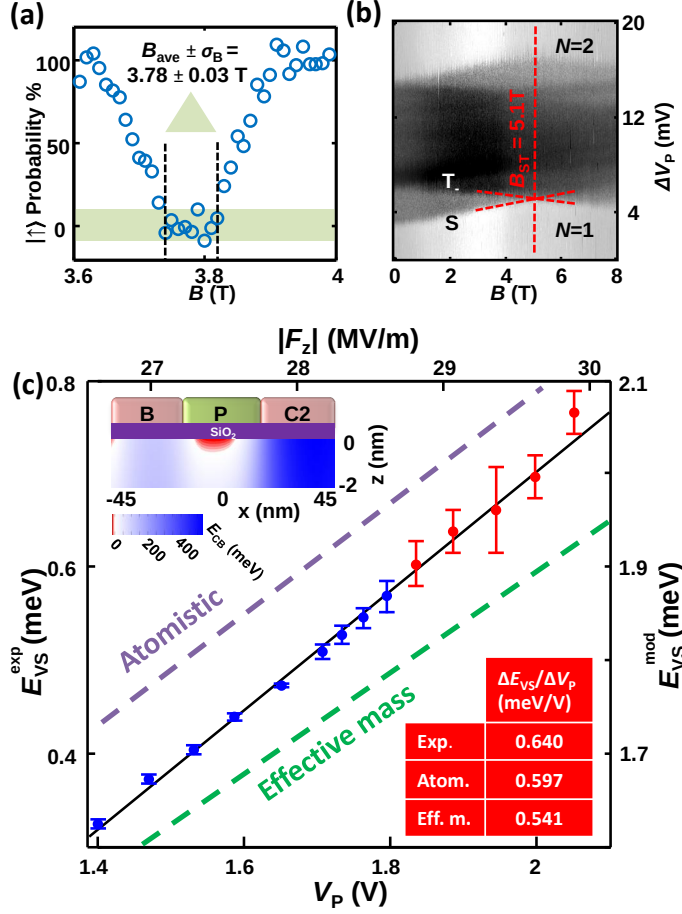


FIG. 4: Tunability of the valley splitting via gate-voltage control. (a) Spin-up probability as a function of magnetic field for $V_P = 1.59$ V. The occurrence of a HS minimizes the spin-up fraction and allows one to extract B_{HS} (shaded area) and, in turn, E_{VS} . (b) Pulsed-voltage magnetospectroscopy showing dI_{SET}/dV_P at $N = 1 \rightarrow 2$ transition. A square pulse of amplitude 16 mV at 287 Hz is applied to gate P. The evolution of the energy difference between the singlet state (light grey) and the triplet state (dark grey) allows one to extract B_{ST} (dashed line) and, in turn, E_{VS} . (c) Valley splitting as a function of plunger gate voltage (bottom axis) and modulus of interface vertical electric field in the QD (top axis). Blue and red dots show the valley separation (left axis) measured with HS and magnetospectroscopic techniques, respectively. The linear fit (solid line) indicates a valley tunability of 0.640 meV/V. Dashed lines are calculations performed via atomistic (purple) and effective mass (green) methods (right axis). Bottom inset: Table comparing calculated and experimental tunabilities. Top inset: TCAD simulation of the conduction band profile at $V_P=1.4$ V in the (x, z) plane. Negative energy region in red reveals where the dot is formed.

dependence for MOS-based QDs⁴⁵ has also been reported by employing atomistic tight-binding calculations⁴⁶. In order to compare our experimental finding with the theoretical predictions, we simulate the vertical electric field (F_z) in the vicinity of the dot for the range of gate voltages used in the experiments. We employ the commercial semiconductor software ISE-TCAD⁴⁷ to model the device electrostatic potential, and thereby the electric fields in the nanostructure. For this purpose, TCAD solves the Poisson equation with an approximation of Newton's iterative method⁴⁸ to obtain convergence at low temperatures.

The spatial extent of the dot is identified by regions where the calculated conduction band energy drops below the Fermi level [red area in the top inset of Fig.

4(c)]. Note that our calculations are performed on a three-dimensional geometry identical to the real device with the only free parameter being the amount of offset interface charge. This is adjusted to match the experimental threshold voltage of the device ($V_{\text{th}}=0.625$ V).

The computed variation of interface electric field with gate voltage V_P is used to determine the valley splitting according to both the atomistic⁴⁵ and effective mass⁷ predictions. Dashed lines in Fig. 4 (c) depict the trends for both approaches, with both exceeding by more than 1 meV the measured values. Despite this offset, the atomistic calculations give a tunability of the valley splitting with gate voltage, $\Delta E_{\text{VS}}/\Delta V_P$, in good agreement with the experiments. The calculated value of 597 $\mu\text{eV/V}$ agrees with the measured value to within less than 7%.

The value of $541 \mu\text{eV}/\text{V}$ calculated using the effective mass approach reveals a larger deviation ($\approx 15\%$) from the experiments. The presence of an offset in the computed valley splitting may be due to the contribution of surface roughness that is not accounted for in the models, and is thought to be responsible for a global reduction of E_{VS} ^{8,10–12,49,50}. We emphasize, however, that the gate tunability would remain robust against this effect, which is not dependent on electric field.

V. CONCLUSIONS

In this work, we have shown that the valley splitting in a silicon device can be electrostatically controlled by simple tuning of the gate bias. We used this valley splitting control, together with spin relaxation measurements, to explore the interplay between spin and valley levels in a few-electron quantum dot.

The relaxation rates for a one-electron system exhibit a dramatic hot-spot enhancement when the spin Zeeman energy equals the valley splitting, while for a two-electron system the rates reach a minimum at this condition. We found that the known mechanisms for spin relaxation, such as the admixing of spin and $2p$ orbital states, were unable to explain the key features of the experimental lifetime data, and so introduced a new paradigm that includes admixing of valley and spin eigenstates. Our theory, which showed good agreement with experiment, implies that spin relaxation via phonon emission due to spin-orbit coupling can occur in realistic quantum dot systems, most likely due to interface disorder.

Our results show that by tuning of the valley splitting in silicon quantum dots, it is possible to always ensure the long lifetimes ($T_1 > 1 \text{ s}$) required for robust spin qubit operation. Despite this, the excited valley state will generally be lower than orbital states in small quantum dots, placing an ultimate limit on the lifetimes accessible in very small dots, due to the spin-valley mixing described above.

Electrical manipulation of the valley states is also a fundamental requirement to perform coherent valley operations. Hence, this work may pave the road for the implementation of recently proposed valley-based qubits^{19,20}. The experimental relaxation rate at the observed hot-spot was found to be fast ($T_1^{-1} > 1 \text{ kHz}$) for our devices, implying a fast inter-valley relaxation rate, so strategies to reduce this would need to be developed.

Finally, in the context of realizing scalable quantum computers, these results allow us to address questions of device uniformity and reproducibility with greater optimism. Indeed, our work suggests that issues related to the wide variability of the valley splitting observed in silicon nanostructures to date can shift from the elusive atomic level (surface roughness, strain, interface disorder) to the more accessible device level, where gate geometry and electrostatic confinement can be engineered to ensure robust qubit systems.

VI. METHODS

The samples fabricated for these experiments are silicon MOS planar structures. The high purity, near intrinsic, natural isotope silicon substrate has n^+ ohmic regions for source/drain contacts defined via phosphorous diffusion. High quality SiO_2 gate oxide is 8 nm thick and is grown by dry oxidation at 800°C . The gates are defined by electron-beam lithography, Al thermal evaporation and oxidation. Three layers of Al/ Al_2O_3 are stacked and used to selectively form a 2DEG at the Si/ SiO_2 interface and provide quantum confinement in all the three dimensions.

Measurements are carried out in a dilution refrigerator with a base temperature $T_b \approx 40\text{mK}$. Flexible coaxial lines fitted with low-temperature low-pass filters connect the device with the room-temperature electronics. In order to reduce pick-up noise, the gates are biased via battery powered and opto-isolated voltage sources. The SET current is amplified by a room-temperature transimpedance amplifier and measured via a fast digitizing oscilloscope and a lock-in amplifier for the single-shot and energy spectrum experiments, respectively. Gate voltage pulses are produced by an arbitrary wave-function generator and combined with a DC offset via a room-temperature bias-tee.

ACKNOWLEDGMENTS

The authors thank D. Culcer for insightful discussions, and F. Hudson and D. Barber for technical support. This work was supported by the Australian National Fabrication Facility, the Australian Research Council (under contract CE110001027), and by the U.S. Army Research Office (under contract W911NF-08-1-0527). The use of nanoHUB.org computational resources operated by the Network for Computational Nanotechnology funded by the US National Science Foundation under grant EEC-0228390 is gratefully acknowledged.

FINANCIAL INTERESTS

The authors declare no competing financial interests.

AUTHOR CONTRIBUTIONS

C.H.Y. carried out the measurements. N.S.L. designed and fabricated the device. C.H.Y., A.R. analyzed the data. C.H.Y., A.R., S.L., G.K., A.M., A.S.D. discussed the results. R.R., C.T. modelled the relaxation rates. F.M. simulated the electric field profiles. A.S.D. conceived and planned the project. A.R. wrote the manuscript with input from all coauthors.

-
- * Electronic address: a.rossi@unsw.edu.au
- ¹ Kane, B. E. A silicon-based nuclear spin quantum computer. *Nature* **393**, 133-137 (1998).
 - ² Maune, B. M. *et al.* Coherent singlet-triplet oscillations in a silicon-based double quantum dot. *Nature* **481**, 7381 (2012).
 - ³ Pla, J. J. *et al.* A single-atom electron spin qubit in silicon. *Nature* **489**, 541-545 (2012).
 - ⁴ Tyryshkin, A. M. *et al.* Electron spin coherence exceeding seconds in high-purity silicon. *Nature Mat.* **11**, 143 (2012).
 - ⁵ Ando, T., Fowler, A. B. & Stern, F. Electronic properties of two-dimensional systems. *Rev. Mod. Phys.* **54**, 437 (1982).
 - ⁶ Sham, L. J. & Nakayama, M. Effective-mass approximation in the presence of an interface. *Phys. Rev. B* **20**, 734 (1979).
 - ⁷ Saraiva, A. L. *et al.* Intervalley coupling for interface-bound electrons in silicon: An effective mass study. *Phys. Rev. B* **84**, 155320 (2011).
 - ⁸ Saraiva, A. L. *et al.* Physical mechanisms of interface-mediated intervalley coupling in Si. *Phys. Rev. B* **80**, 081305(R) (2009).
 - ⁹ Boykin, T. B. *et al.* Valley splitting in strained silicon quantum wells. *Appl. Phys. Lett.* **84**, 115 (2004).
 - ¹⁰ Friesen, M., Chutia, S., Tahan, C. & Coppersmith S. N. Valley splitting theory of SiGe/Si/SiGe quantum wells. *Phys. Rev. B* **75**, 115318 (2007).
 - ¹¹ Ando, T. Valley splitting in the silicon inversion layer: Misorientation effects. *Phys. Rev. B* **19**, 3089 (1979).
 - ¹² Friesen, M., Eriksson, M. A. & Coppersmith, S. N. Magnetic field dependence of valley splitting in realistic Si/SiGe quantum wells. *Appl. Phys. Lett.* **89**, 202106 (2006).
 - ¹³ Goswami, S. *et al.* Controllable valley splitting in silicon quantum devices. *Nature Phys.* **3**, 41-45 (2007).
 - ¹⁴ Lansbergen, G. P. *et al.* Lifetime-Enhanced Transport in Silicon due to Spin and Valley Blockade. *Phys. Rev. Lett.* **107**, 136602 (2011).
 - ¹⁵ Roche, B. *et al.* Detection of a large valley-orbit splitting in silicon with two-donor spectroscopy. *Phys. Rev. Lett.* **108**, 206812 (2012).
 - ¹⁶ Takashina, K., Ono, Y., Fujiwara, A., Takahashi, Y. & Hiramaya, Y. Valley Polarization in Si(100) at Zero Magnetic Field. *Phys. Rev. Lett.* **96**, 236801 (2006).
 - ¹⁷ Culcer, D., Cywiński, L., Li, Q., Hu, X. & Das Sarma, S. Realizing singlet-triplet qubits in multivalley Si quantum dots. *Phys. Rev. B* **80**, 205302 (2009).
 - ¹⁸ Li, Q., Cywiński, L., Culcer, D., Hu, X. & Das Sarma, S. Exchange coupling in silicon quantum dots: Theoretical considerations for quantum computation. *Phys. Rev. B* **81**, 085313 (2010).
 - ¹⁹ Smelyanskiy, V. N., Petukhov, A. G. & Osipov, V. V. Quantum computing on long-lived donor states of Li in Si. *Phys. Rev. B* **72**, 081304 (2005).
 - ²⁰ Culcer, D., Saraiva, A. L., Koiller, B., Hu, X. & Das Sarma, S. Valley-Based Noise-Resistant Quantum Computation Using Si Quantum Dots. *Phys. Rev. Lett.* **108**, 126804 (2012).
 - ²¹ Xiao, M., House, M. G. & Jiang, H. W. Measurement of the Spin Relaxation Time of Single Electrons in a Silicon Metal-Oxide-Semiconductor-Based Quantum Dot. *Phys. Rev. Lett.* **104**, 096801 (2010).
 - ²² Simmons, C. B. *et al.* Tunable Spin Loading and T_1 of a Silicon Spin Qubit Measured by Single-Shot Readout. *Phys. Rev. Lett.* **106**, 156804 (2011).
 - ²³ Hayes, R. R. *et al.* Lifetime measurements (T_1) of electron spins in Si/SiGe quantum dots. Preprint at <http://arxiv.org/abs/0908.0173> (2009).
 - ²⁴ Morello, A. *et al.* Single-shot readout of an electron spin in silicon. *Nature* **467**, 687 (2010).
 - ²⁵ Zwanenburg, F. A. *et al.* Silicon Quantum Electronics. Preprint at <http://arxiv.org/abs/1206.5202> (2012).
 - ²⁶ Bulaev, D. V. & Loss, D. Spin relaxation and anticrossing in quantum dots: Rashba versus Dresselhaus spin-orbit coupling. *Phys. Rev. B* **71**, 205324 (2005).
 - ²⁷ Raith, M., Stano, P. & Fabian, J. Theory of single electron spin relaxation in Si/SiGe lateral coupled quantum dots. *Phys. Rev. B* **83**, 195318 (2011).
 - ²⁸ Hanson, R. *et al.* Spins in few-electron quantum dots. *Rev. Mod. Phys.* **79**, 1217 (2007).
 - ²⁹ Angus, S. J., Ferguson, A. J., Dzurak, A. S. & Clark, R. G. Gate-Defined Quantum Dots in Intrinsic Silicon. *Nano Lett.* **7**, 2051 (2007).
 - ³⁰ Elzerman, J. M., Hanson, R., Willems van Beveren, L. H., Vandersypen, L. M. K. & Kouwenhoven, L. P. Excited-state spectroscopy on a nearly-closed quantum dot via charge detection. *Appl. Phys. Lett.* **84**, 23 (2004).
 - ³¹ Yang, C. H., Lim, W. H., Zwanenburg, F. A. & Dzurak, A. S. Dynamically controlled charge sensing of a few-electron silicon quantum dot. *AIP Advances* **1**, 042111 (2011).
 - ³² Kouwenhoven, L. P., Austing, D. G. & Tarucha, S. Few-electron quantum dots. *Rep. Prog. Phys.* **64**, 701 (2001).
 - ³³ Tarucha, S., Austing, D. G., Honda, T., van der Hage, R. J. & Kouwenhoven, L. P. Shell Filling and Spin Effects in a Few Electron Quantum Dot. *Phys. Rev. Lett.* **77**, 3613 (1996).
 - ³⁴ Borselli, M. G. *et al.* Measurement of valley splitting in high-symmetry Si/SiGe quantum dots. *Appl. Phys. Lett.* **98**, 123118 (2011).
 - ³⁵ Elzerman, J. M. *et al.* Single-shot read-out of an individual electron spin in a quantum dot. *Nature* **430**, 431 (2004).
 - ³⁶ Glavin, B. A. & Kim, K. W. Spin-lattice relaxation in Si quantum dots. *Phys. Rev. B* **68**, 045308 (2003).
 - ³⁷ Tahan, C., Friesen, M. & Joint, R. Decoherence of electron spin qubits in Si-based quantum computers. *Phys. Rev. B* **66**, 035314 (2002).
 - ³⁸ Tahan, C. Doctoral Dissertation, University of Wisconsin-Madison, (2005). Preprint at <http://arxiv.org/abs/0710.4263>
 - ³⁹ Stano, P. & Fabian, J. Theory of Phonon-Induced Spin Relaxation in Laterally Coupled Quantum Dots. *Phys. Rev. Lett.* **96**, 186602 (2006).
 - ⁴⁰ Stano, P. & Fabian, J. Orbital and spin relaxation in single and coupled quantum dots. *Phys. Rev. B* **74**, 045320 (2006).
 - ⁴¹ Yang, C. H. *et al.* Orbital and valley state spectra of a few-electron silicon quantum dot. *Phys. Rev. B* **86**, 115319 (2012).
 - ⁴² Wilamowski, Z., Jantsch, W., Malissa, H. & Rossler, U. Evidence and evaluation of the Bychkov-Rashba effect in SiGe/Si/SiGe quantum wells. *Phys. Rev. B* **66**, 195315 (2002).
 - ⁴³ Nestoklon, M. O., Golub, L. E. & Ivchenko, E. L. Spin and valley-orbit splittings in SiGe/Si heterostructures. *Phys.*

- Rev. B* **73**, 235334 (2006).
- ⁴⁴ Wang, L., Shen, K., Sun, B. Y. & Wu, M. W. Singlet-triplet relaxation in multivalley silicon single quantum dots. *Phys. Rev. B* **81**, 235326 (2010).
- ⁴⁵ Lee, S. Doctoral Dissertation, Purdue University (2011).
- ⁴⁶ Klimeck, G. *et al.* Atomistic simulation of realistically sized nanodevices using NEMO 3-D - Part II: Applications *IEEE Trans. Elec. Dev.* **54**, 2090 (2007).
- ⁴⁷ Integrated System Engineering, Dessis v10 Manual, Zurich (2004).
- ⁴⁸ Bank, R. E. & Rose, D. J. Global approximate Newton methods. *Numerische Mathematik* **37**, 279 (1981).
- ⁴⁹ Culcer, D., Hu, X. & Das Sarma, S. Interface roughness, valley-orbit coupling, and valley manipulation in quantum dots. *Phys. Rev. B* **82**, 205315 (2010).
- ⁵⁰ Friesen, M. & Coppersmith, S. N. Theory of valley-orbit coupling in a Si/SiGe quantum dot. *Phys. Rev. B* **81**, 115324 (2010).